

CHASM Ag^eNT™-1 G3

Hybrid Transparent Conductive Films



PRODUCT DESCRIPTION

Ag^eNT-1-G3 is a Nanotube Hybrid Transparent Conductive Film (TCF) made by printing proprietary Ag^eNT ink formulated with conductive carbon nanotubes onto a Metal Mesh (MM) film. Delivering comparatively more robust and uniform conductivity at higher transparency, this exclusive category of flexible TCF performs substantially better than TCFs comprised of CNTs or MM alone.

HOW AG^eNT™ WORKS

Nanotube ink is formulated for screen printing and is comprised of a mixture of our single-walled nanotubes (Co- MoCATTM technology), an optically clear polymer binder and our proprietary ink vehicle (V2VTM technology). The grade of CNT ink used for making Ag^eNT-1 product structures is CHASM- AGENT-VC201.

The MM film is comprised of a copper (Cu) mesh in a diamond-shape patterned onto 100µm thick PET film. Thickness of the Cu is 2µm with a line width and pitch of 5µm & 100µm respectively. The grade of MM film used for making Ag^eNT-1-MM-G3 product structures is CHASM-AGENT-AM310.

Ag^eNT-1-G3 film is available in standard sheet size of approximately 457mm X 605mm. Alternative sheet sizes as large as 605mm X 1,030mm or in roll form at 605mm wide is also available upon request. Ag^eNT inks are available in standard 1L bottles. Please note minimum trace width is 1mm and minimum gap width is 0.15mm.

CONTACT INFORMATION


Headquarters & Applications Development Center

480 Neponset Street – Bldg. 6
Canton, MA 02021
O: (781) 821-0443 F: (781) 821-0447

Manufacturing Plant and R&D Center

2501 Technology Place
Norman, OK 73071

ENVIRONMENTAL

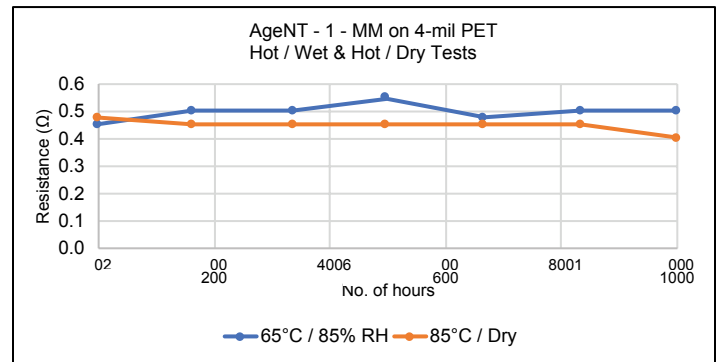

Resistance, adhesion and optical properties exhibit very stable behavior with environmental aging.

OPTOELECTRONIC PROPERTIES

	TCF + Substrate	TCF only
Sheet Resistance (Ω/□)	0.2	0.2
VLT (%)	78.1%	84.4%
Haze (%)	5.0%	3.5%
L*	93.91	-
a*	-0.11	-
b*	1.34	-

Optical properties measured by R-chek 4-point resistance meter, BYK Hazegard transparency meter or X-Rite spectrophotometer.

SALES INQUIRIES OR PRODUCT QUESTIONS

North America

Al Tassone
atassone@chasmtek.com

Europe

Tom Eldridge
teldridge@chasmtek.com

Asia

Chel Shen
cshen@chasmtek.com

Sales & Tech Support: +1 781.821.0443

www.chasmtek.com

CHASM AgeNT™-1-G3

Hybrid Transparent Conductive Films




AGENT-1-G3 STACK

PE Release Liner
VC201 Ink plus $0.2\Omega/\square$ Cu MM
4 mil PET Film
PE Release Liner

AM310



AgeNT-1 Film: Diamond pattern consists of $5\mu\text{m}$ lines of $2\mu\text{m}$ thick Cu having a $100\mu\text{m}$ pitch for ~ 85% open area

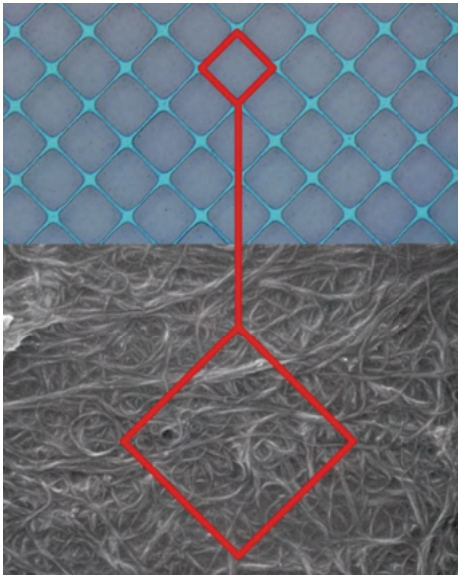

Nanotubes bridge across open areas making them conductive.

PRODUCT BENEFITS

- Extremely low sheet resistance with high optical transparency
- Low materials and processing costs for creating patterned TCFs
- Thin & flexible – can be easily be attached to flat or curved plastic or glass surfaces with OCA film
- Resistance, adhesion and optical properties are very stable with environmental aging.

TARGET APPLICATIONS

Applications include transparent RF antennas, transparent heaters, transparent RF / EMI shielding, transparent wiring for micro-LEDs, etc.

- Transparent Antennas Application requiring the support for mm wave
- Transparent NFC Antennas
- Transparent EMI/RF Shielding
- Transparent Heaters
- Transparent Electrodes for Lighting

SUPPORTING DATA

Flexible printed circuit (FPC) patterns are created by:

1. screen printing CNT ink on top of the MM film;
2. hot air drying at $\sim 100^\circ\text{C}$;
3. chemically etching the exposed Cu mesh areas.

Typical etchants include Ferric Chloride (industry standard for Cu etching) or Ferric Nitrate.

This affordable circuit patterning process is suitable for mass production and is referred to as “Print / Etch / Done”. Having fewer processing steps and creating less waste streams than photolithographic etching or laser ablation, “Print / Etch / Done” is faster and more cost effective.

AgeNT ink is a multi-functional material acting as both a printed etch mask for low-cost patterning and also as an encapsulate of the MM delivering superior environmental stability. TCFs created from CHASM Nanotube Hybrids are more robust and uniformly conductive for the best printed electronics you’ll never see.

AgeNT-1-G3: $0.2\Omega/\square$ at $>84\%$ VLT

DISCLAIMER

The information provided in this Technical Data Sheet (TDS) including the recommendations for use and application of the product are based on CHASM's accumulated experience as of the date of publication. Product performance will vary based on application and operational environment, so CHASM Advanced Materials Inc. is not liable for the suitability of our product for the intended applications and results.

Several patents issued & pending. AgeNT, the AgeNT logo, CHASM, the CHASM logo, CoMoCAT and V2V are trademarks of CHASM Advanced Materials, Inc. Copyright © 2020 CHASM Advanced Materials, Inc., all rights reserved.